

## Research Article

# Comparative Evaluation of the Shear Bond Strength and De-bonding Properties of Self-Etch Adhesive Composite Cement (Maxcem Elite Chroma) vs. Self-Etching Primer Composite System (Transbond Plus Sep, 3M Unitek, Monrovia, Calif) used for Orthodontic Bracket Bonding

Sameer Ahmad Malik\* and Laxmikanth SM

Department of Orthodontics, AECS Maaruti College of Dental Sciences and Research Center, India

## Abstract

**Background:** Over the last 50 years the bonding of various adhesives to enamel and dentin has developed a niche in nearly all areas of dentistry, including orthodontics. Combining conditioning and priming into a single step improves bonding time and cost-effectiveness to the clinician and Orthodontists use the acid-etch bonding technique to attach brackets to the enamel surface. Maintaining a sound, unblemished enamel surface after de-bonding the brackets is a primary concern to the clinician. Self-adhesive cements were introduced in 2002 as a new subgroup of resin cements. Self-adhesive cements do not require any pre treatment of the tooth surface. Once the cement is mixed, its application is a single clinical step. Sufficient research is not available with regard to whether self etching adhesives can be satisfactorily used in the field of orthodontics to bond the brackets. Maxcem Elite Chroma (Kerr Dental) is a self-etch/self-adhesive resin cement with a Colour Cleanup Indicator. The use of Maxcem Elite Chroma in the field of orthodontics is rather unexplored. Its basic properties such as SBS, the de-bonding properties and its effect on enamel demineralization need to be evaluated to commend its use for bonding in orthodontics.

**Aims and objective:** Comparative evaluation of the shear bond strength and de-bonding properties of self etch adhesive composite cement (Maxcem Elite Chroma) versus self etching primer composite system (Transbond Plus SEP, 3M Unitek, Monrovia, Calif) used for orthodontic bracket bonding.

**Materials and methods:** This was an in vitro study, conducted in controlled laboratory settings. Forty extracted human premolars extracted for purpose of orthodontic treatment. 20 premolars bonded with orthodontic brackets using the self-etch primer Transbond Plus (3M Unitek) containing both the acid and the primer by following manufacturer's recommendation and 20 premolars bonded with orthodontic brackets using the self-etching composite adhesive (Maxcem Elite™ Chroma Self-etch/Self-adhesive Resin Cement) cement by following manufacturer's recommendation. Results of continuous measurements were presented as mean ± SD. Significance was assessed at 5% level of significance at 95% confident interval. Mann Whitney U test was used to compare the shear bond strength of self-etching composite adhesive to self etch primer. Chi square test was used to evaluate the differences in ARI scores among both the groups. Chi square test showed that there were statistically significant differences among the groups ( $p < 0.001$ ).

**Results:** Maxcem elite chroma exhibited the highest mean shear bond strength of 25.7 MPa and Transbond Plus (3M Unitek, Monrovia, CA, USA) exhibited the mean shear bond strength of 18.7 MPa. Maxcem elite chroma exhibited the highest ARI index thereby demonstrating its better de-bonding properties.

**Conclusion:** Within the limitations of the current study we concluded that: 1. New self-etch, self-adhesive bonding system surprisingly showed high SBS as compared to self etch primer, 2. It also demonstrated a high ARI scores on the bracket surface which signifies that the de-bonding takes place mostly at tooth resin interface thereby reduces the chances of deleterious effects like crazing of enamel surface from de-bonding forces.

**Keywords:** Bonding; Shear bond strength; Adhesive remnant index; Self etch bonding agent and Self etch adhesive resin cements

**Citation:** Malik SA, Laxmikanth SM. Comparative Evaluation of the Shear Bond Strength and De-bonding Properties of Self-Etch Adhesive Composite Cement (Maxcem Elite Chroma) vs. Self-Etching Primer Composite System (Transbond Plus Sep, 3M Unitek, Monrovia, Calif) used for Orthodontic Bracket Bonding. Dentist. 2019; 1(2): 1007.

**Copyright:** © 2019 Sameer Ahmad Malik

**Publisher Name:** Medtext Publications LLC

**Manuscript compiled:** August 7<sup>th</sup>, 2019

**\*Corresponding author:** Sameer Ahmad Malik, Department of Orthodontics, AECS Maaruti College of Dental Sciences and Research Center, Bangalore, India, Tel: 918553340994, 917019335712; E-mail: malik11sameer@gmail.com

## Introduction

Over the last 50 years the bonding of various adhesives to enamel and dentin has developed a niche in nearly all areas of dentistry, including orthodontics.

Adhesion currently encompasses a combination of mechanical, adsorption, diffusion, and electrostatic phenomena [1]. Conventional adhesive systems use three different agents-an enamel conditioner, a primer solution, and an adhesive resin to bond orthodontic brackets to enamel.

A unique characteristic of some bonding systems in operative dentistry is that they combine the conditioning and priming agents into a single acidic primer solution for simultaneous use on both enamel and dentin Combining conditioning and priming into a

single step improves bonding time and cost-effectiveness to the clinician and indirectly to the patient [2,3]. These systems were used originally on dentin. Essentially, the acidic part of the primer dissolves the smear layer and incorporates it into the mixture [3,4]. Acidic primer solutions also demineralise the dentin and encapsulate the collagen fibres and hydroxyapatite crystals. This simultaneous conditioning and priming allows penetration of the monomer into the dentin [5]. The adhesive resin component will then diffuse into the primed dentin, producing a “hybrid layer. While these conditioners were initially developed for use on dentin, studies have determined that adhesive systems combining conditioning and priming were also found to be effective when bonding to enamel [5,6].

Orthodontists use the acid-etch bonding technique to attach brackets to the enamel surface. Maintaining a sound, unblemished enamel surface after de-bonding the brackets is a primary concern to the clinician. As a result, bond failure at the bracket-adhesive interface or within the adhesive is more desirable (safer) than at the adhesive-enamel interface, because enamel fracture and crazing have been reported at bracket de-bonding especially with ceramic brackets. It is possible that the depth of the etched enamel surface created by phosphoric acid may be a factor contributing to the incidence of enamel fracture [7]. Therefore, alternative enamel conditioners, such as maleic acid, and the newly introduced acidic primers that contain phenyl P may be beneficial, if they can maintain clinically useful orthodontic bracket bond strength while decreasing the depth of enamel dissolution [8-10].

Until recently, resin cements were divided into these two subgroups according to the adhesive system used to prepare the tooth prior to cementation. One group utilizes etch-and rinse adhesive in the other group, enamel and dentin are prepared using self-etching primers.

Self-adhesive cements were introduced in 2002 as a new subgroup of resin cements. These materials were designed with the intent to overcome some of the shortcomings of both conventional (zinc phosphate, polycarboxylate, and glass-ionomer cements) and resin cements, as well as to bring the favourable characteristics of different cement classes into a single product.

Self-adhesive cements do not require any pre treatment of the tooth surface. Once the cement is mixed, its application is a single clinical step, similar to the application procedures of zinc-phosphate and polycarboxylate cements. These are still relatively new and detailed information on their composition and adhesive properties is limited. Although the basic adhesion mechanism appears to be the same for all self-adhesive cements, its multifunctional monomers with phosphoric acid groups simultaneously demineralise and infiltrate enamel and dentin. The dominant setting reaction is the radical polymerization that can be initiated by light exposure or through the self-curing mechanism. As the smear layer is not removed, no postoperative sensitivity is expected. Self-adhesive cements are claimed to be moisture tolerant.

It has been demonstrated that Shear Bond Strengths (SBSs) of brackets bonded using different “Self-Etch” Primers (SEPs) were not significantly different from those associated with brackets bonded with the conventional acid-etch technique. It has also been concluded that SEPs that produce a minimal etch pattern can still provide adequate bracket SBS [9-11]. Additionally, it was observed that when using a self-etching adhesive to bond brackets, no significant

difference was seen when the SEP was cured either in separate steps or simultaneously with the bonding adhesive [12].

Sufficient research is not available with regard to whether self etching adhesives can be satisfactorily used in the field of orthodontics to bond the brackets. The SBS, the de-bonding properties and its effect on enamel demineralization have been documented rather elusively [13].

Maxcem Elite Chroma (Kerr Dental) is a self M etch/self M adhesive resin cement with a Colour Cleanup Indicator, to tell the optimal window of time to clean up excess cement. The use of Maxcem Elite Chroma in the field of orthodontics is rather unexplored. Its basic properties such as SBS, the de-bonding properties and its effect on enamel demineralization need to be evaluated to commend its use for bonding in orthodontics.

## Materials and Methods

In this study, the experimental model consisted of 1 control group and 1 experimental groups:

**Group 1: Control group:** 20 premolars bonded with orthodontic brackets (Ortho Organizers, MBT 0.022, Carlsbad, USA) using the self-etch primer Transbond Plus (3M Unitek) containing both the acid and the primer by following manufacturer’s recommendation.

**Group 2: Experimental group:** 20 premolars bonded with orthodontic brackets (Ortho Organizers, MBT 0.022, Carlsbad, USA) using the self-etching composite adhesive (Maxcem Elite™ Chroma Self-etch/Self-adhesive Resin Cement) cement by following manufacturer’s recommendation.

Forty freshly extracted human premolars extracted for the purpose of orthodontic treatment were collected and stored in a solution of 0.1% (wt/vol) thymol.

### Inclusion criteria

1. Extracted human premolar teeth extracted for the purpose of orthodontic treatment will be selected only if they have intact buccal enamel.

### Exclusion criteria

1. Teeth having surface cracks from extraction forceps,
2. Teeth treated with chemical agents, and
3. Teeth having caries or restoration
4. Teeth undergone attrition
5. Teeth previously not tested or bonded for any purposes.

### Groups tested

**Group 1 (control group):** Twenty premolar were bonded using the manufacturer’s recommended protocol then is applied by continuously rubbing the self etch primer Transbond Plus (3M Unitek) on the enamel surface for 3 to 5 seconds. The SEP is then lightly dried using compressed air for 1-2 seconds. Each pre coated bracket was placed on the tooth and held for 10 seconds. The force gauge can be used to help assure a uniform adhesive thickness between the bracket and enamel. The bracket was then light cured using a LED curing light for 20 seconds (10 seconds for each proximal side).

**Group 2 (experimental group):** Twenty premolars were bonded, following the manufacturer’s recommendations, using the self-etchant adhesive (Maxcem Elite™ Chroma Self-etch/Self-adhesive Resin

Cement). Maxcem Elite Chroma was applied on enamel surfaces, and bracket bases were bonded in place without separate enamel etching step before bonding. This self-etch, self adhesive resin cement was polymerized with LED curing light for 20 s each on both mesial and distal sides (i.e., 40 s total).

**Determination of bond strength and de bonding procedure:** Bond strength was determined by a universal testing machine (MecMesin Intelligent Load Unit) with 1 kN load cell at crosshead speed of 1 mm/minute. Each tooth was oriented with the testing device as a guide such that its labial surface was parallel to the force during the shear strength test. An occlusal-gingival load was applied to the bracket with a blade-end steel rod attached to the crosshead of the universal testing machine. This produced a shear force at the bracket-tooth interface. The load at bracket failure was recorded electronically in Newton's by a computer connected to the MecMesin machine. The SBS values were calculated in mega Pascal by dividing the force by the area of the bracket base (MPa=N/mm<sup>2</sup>). The maximum load necessary to debond or initiate bracket fracture was recorded in Newton and then converted into mega Pascal as a ratio of Newton's to the bracket surface area. The bracket surface area of Ortho Organizer maxillary first premolar bracket is 10.27 mm<sup>2</sup>.

**Adhesive remnant index:** After bond failure, the teeth and brackets were examined under 10x magnifications (Table 1). Any adhesive remaining after bracket removal was assessed using a modified Adhesive Remnant Index (ARI) and scored with respect to the amount of resin material adhering to the enamel surface. The ARI scale has a range between 5 and 1:

- Score 0 = no adhesive left on bracket
- Score 1 = less than 25% of adhesive left on bracket
- Score 2 = 25% of adhesive left on bracket
- Score 3 = 50% of adhesive left on bracket
- Score 4 = 75% of adhesive left on bracket
- Score 5 = 100% of adhesive left on bracket

**Statistical analysis:** Results of continuous measurements were presented as mean ± SD. Significance was assessed at 5% level of significance at 95% confident interval. Mann Whitney U test was used to compare the shear bond strength of self-etching composite adhesive to self etch primer.

Chi square test was used to evaluate the differences in ARI scores among both the groups. Chi square test showed that there were statistically significant differences among the groups (p<0.001) (Figure 1-9).


## Results

### Shear bond strength


Mean SBS values (in MPa) of the two test groups and their descriptive statistics are shown in Table 2 and Figure 10 respectively. Maxcem elite chroma exhibited the highest mean shear bond strength of 25.7 MPa and Transbond Plus (3M Unitek, Monrovia, CA, USA) exhibited the mean shear bond strength of 18.7 MPa. The difference

**Table 1:** ARI score as seen in 10X magnification.


Group	Score 0 (%)	Score 1 (%)	Score 2 (%)	Score 3 (%)	Score 4 (%)	Score 5 (%)
<b>TXT (Control)</b>	1 (5)	4 (20)	7 (35)	5 (25)	2 (10)	1 (5)
<b>MEc (Experimental)</b>	0 (0)	1 (5)	2 (10)	7 (35)	6 (30)	4 (5)

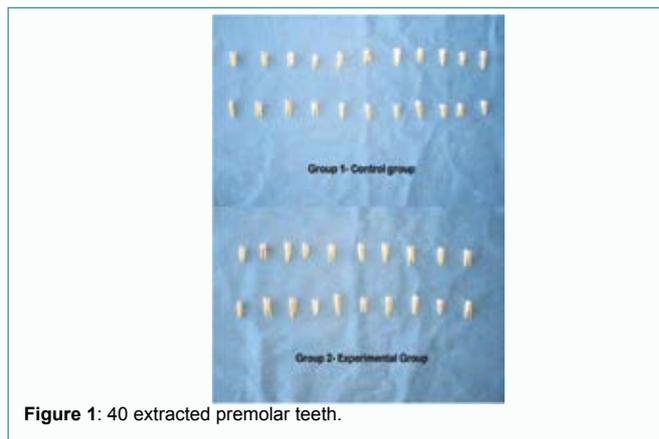


**Figure 1:** 40 extracted premolar teeth.

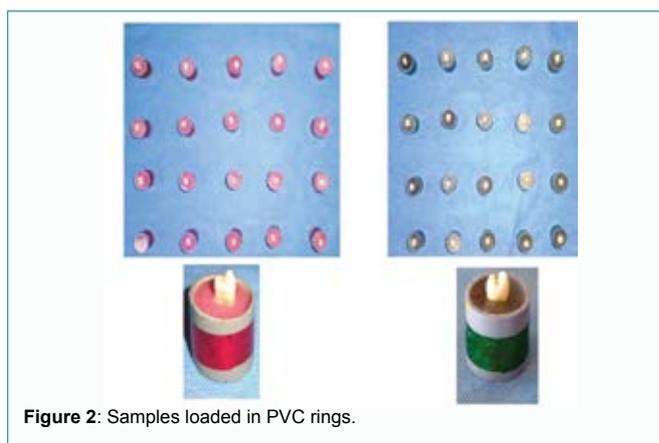

**Figure 2:** Samples loaded in PVC rings.

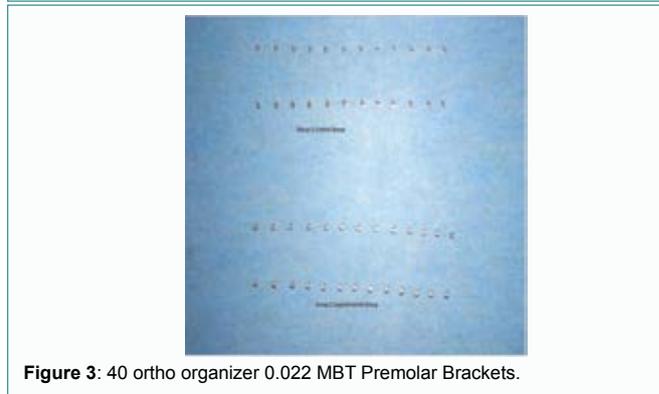

**Figure 3:** 40 ortho organizer 0.022 MBT Premolar Brackets.

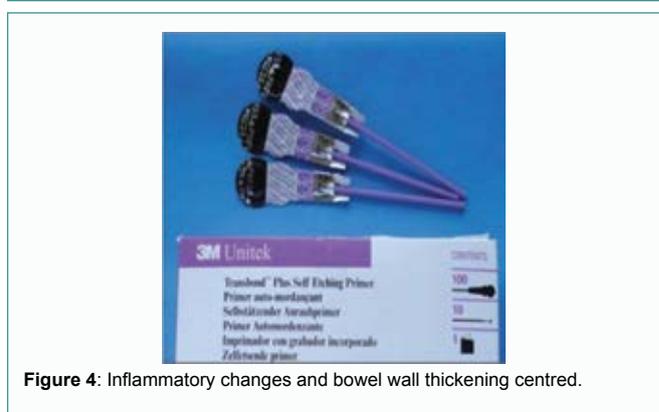

**Figure 4:** Inflammatory changes and bowel wall thickening centred.




**Figure 5:** Syringe 1-Transbond XT Composite. Syringe 2-Maxcem elite chroma SEA.



**Figure 6:** Armamentarium (from left to right).  
1. Bracket holder 2. Explorer 3. Probe 4. Composite handling instrument 5. Contrangle hand piece with rubber cup 6. Pumice 7. Coltene 3M Spec curing L.E.D




**Figure 7** Pumice polishing of buccal surfaces of Premolars followed by bonding.

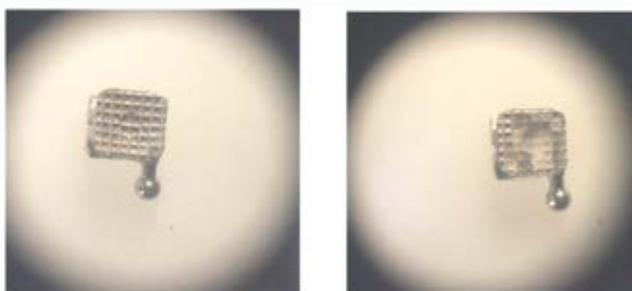

Control group                      Experimental group

**Figure 8:** Adhesive remnant (Microscopy 10X).

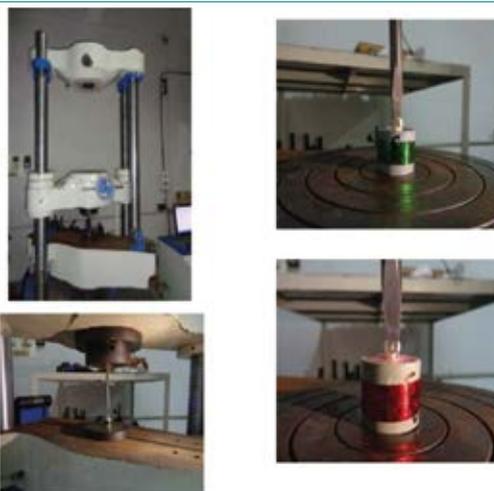

**Figure 9:** Universal Testing Machine for SBS: Fine Testing Machine Model: TFUC-1000.

**Table 2:** Comparison of shear bond strength of Self-etch primer and Self-etching composite.

Shear bond strength Z P [Mean ± SD]			
Self-etching composite adhesive (Experimental)	25.74 ± 1.96	-5.46	0*
Self-etch primer (Control)	18.77 ± 1.64		

Mann-Whitney U,


\*Statistically significant, p<0.05

This table shows that the mean shear bond strength of self-etch primer (18.77 ± 1.64) was less than self-etching composite adhesive (25.74 ± 1.96) and this difference was statistically significant. (p=0.00)

found between the two groups was seen to be statistically significant (p<0.005). Results of continuous measurements were presented as mean ± SD. Significance was assessed at 5% level of significance at 95% confident interval. Mann Whitney U test was used to compare the shear bond strength of self-etching composite adhesive to self etch primer.

**ARI scores**

Table 3 shows comparison of ARI scores among the groups. Figure 11 shows the distributions of ARI scores, by percentage, for all the test groups. Chi square test was used to evaluate the differences in ARI scores among both the groups. Chi square test showed that there were statistically significant differences among the groups (p<0.001).

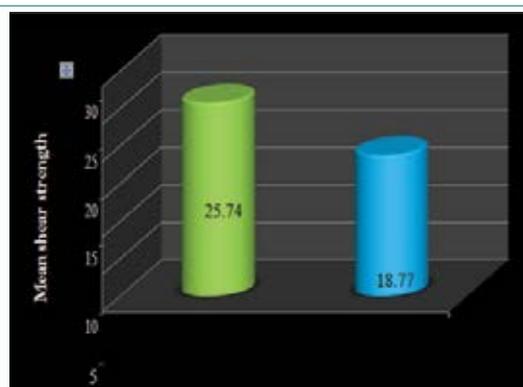

**Figure 10:** Comparison of shear bond strength of Self-etch primer and Self-etching composite adhesive.

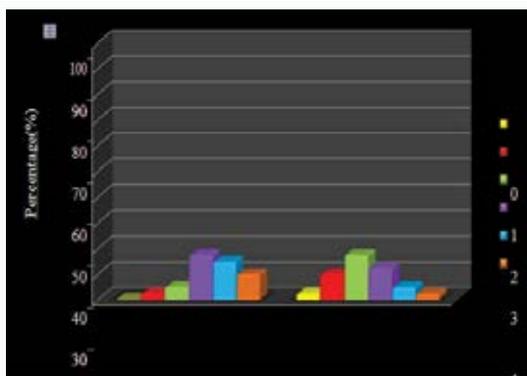


Figure 11: Comparison of ARI scores among the groups.

## Discussion

The direct bonding of orthodontic brackets has revolutionized and advanced the clinical practice of orthodontics. However, there is a need to improve the bonding procedure by saving time and minimizing enamel loss without jeopardizing clinically useful bond strength. Although recent bonding systems have been proven reliable, improvements are still necessary to minimize technique sensitivity and reduce the chair time by decreasing the number of steps during the bonding procedure. Traditionally, using acid etchants followed by a primer was an essential part of the bonding procedure of composite adhesives, to allow good wetting and penetration of the sealant into the enamel surface [10,11]. The use of the new self adhesive resin cements for orthodontic purposes has not yet been fully evaluated. In general, they are thought to simplify the clinical handling of the adhesive systems by combining the etchant, primer and composite resin in 1 application. The present study evaluated 2 adhesive systems-Transbond Plus with a 2-component self-etch primer and Maxcem Elite Chroma self etching adhesive resin cement. The findings indicated that both bonding systems provided adequate shear bond strengths but Maxcem elite chroma exhibited the highest mean shear bond strength of 25.7 MPa and Transbond Plus exhibited the mean shear bond strength of 18.7 MPa. The difference found between the two groups was seen to be statistically significant ( $p < 0.005$ ). This was an in vitro study, and care should be taken in comparing the results with those that might be obtained in the oral environment. In addition, more research is needed to determine the shear bond strength of these new self-etch adhesive

resin cements over a longer time period, e.g. 24 hours and 1 week after bonding and after thermocycling.

### Transbond™ plus self etching primer

Minimum bond strength for clinically acceptable bracket bonding was reportedly MPa12 [6-8]. In the present study, Transbond XT self-etch resin materials showed clinically acceptable bond strengths for bracket bonding. It has been proved in many studies that the SBS of Transbond XT SEP is comparable to conventional Transbond XT. Transbond XT is a traditional composite resin filled with filler particles of diverse sizes<sup>13</sup> and which reportedly exhibited clinically acceptable bond strength values. Transbond XT was used as the gold standard in many SBS studies [12-42]. However, its SBS values varied widely between  $8.9 \pm 3.9$  and  $18.1 \pm 5.5$  MPa in literature. Mineral structures of the teeth used in these studies might have an effect on the SBS of different bonding agents, thus accounting for this large disparity in the SBS data of Transbond XT. Secondly, pressure exerted by the hand piece instrument during polishing might have an effect on tooth surface features, which would then affect the SBS of adhesive materials (Table 4) and cause differences in the SBS of Transbond XT among different studies.

### Phosphoric acid etchant versus self-etch adhesive systems

Pretreatment with 37% phosphoric acid increases bond strength because thick outer enamel layer may prevent the permeation of self-etch primers and bonding agents, thus leaving some areas partially unetched [43,44]. This then results in formation of shorter and poorly defined resin tags. By removing the outer enamel with phosphoric acid etching, longer resin tags are formed and thus bond strength is increased [45]. On the other hand, self-etch primers and bonding agents have some advantages over the phosphoric acid etchant. Self-etch primers simplify the clinical handling of adhesive systems by combining the conditioning and priming agents into a single product [4,5]. Self-etch bonding agents prevent aggressive decalcification and bulk enamel loss which are characteristics of phosphoric acid etching [46]. This means that they reduce the risk of enamel damage due to their reduced ability to sufficiently etch and penetrate the enamel surface [47]. Most self-etch adhesives did not etch enamel as deeply as the phosphoric acid etchants did, but the shallow etching pattern compromised bonding to enamel [48]. Demineralization effects of self-etch primers and bonding agents are proportional to their acidity [49]. The lower the pH, the higher the acidity, the deeper the etch;

Table 3: Comparison of ARI scores among the groups.

GROUPS	ARI scores (%)							Chi-square	P
	0	1	2	3	4	5	Total		
Self-etching composite adhesive (Experimental)	0	2.5	5	17.5	15	10	50	9.711	0.1
Self-etch primer (Control)	2.5	10	17.5	12.5	5	2.5	50		
Total	2.5	12.5	22.5	30	20	12.5	100		

\*Statistically significant,  $p < 0.05$

This table shows that majority (30%) of samples had score 3 followed by score 2(22.5%) and score 4(20%). In the experimental group, majority (35%) of samples had score 3 followed by score 4(30%) and score 5(20%). In the control group, majority (35%) of participants had score 2 followed by score 3(25%) and score 1(20%). However there was no significant difference between them. ( $p = 0.08$ ).

Table 4: Compositions of adhesive materials used in this study.

Adhesive material	Manufacturer	Filler	Weight composition
Transbond XT Light-cure adhesive with self etch primer	3M Unitek, Monrovia, CA, USA	80	phosphoric 35% acid, silanetreated quartz, bisphenol A diglycidyl ether dimethacrylate, A bisphenol bis-(2-hydroxyethyl)-ether dimethacrylate, silane treated silica
Maxcem Elite Chroma Self-etch, self-adhesive Glycerol dim	Kerr Italia, 84018 Scafati, Italy	69	Methacrylate GPDM, ester monomers, HEMA, cumene 4 methoxyphenol, hydroperoxide, titanium dioxide and pigments

GPDM: Glycerol Dimethacrylate Dihydrogen Phosphate; HEMA: 2-Hydroxyethyl Methacrylate; MEHQ: Monomethyl Ether Hydroquinone

and the pH values of self-etch adhesive systems are higher than that of phosphoric acid etchant. Self-etch adhesive systems produce high bond strengths to human coronal dentin and ground enamel surfaces [50]. With enamel, phosphoric acid pre treatment improved the bond strength; with dentin, prior acid etching was detrimental to dentin bonding effectiveness and should be avoided [51,52]. Self-etch adhesives have high viscosity, which causes an incomplete resin decrease in its bracket retentive ability.

### Maxcem elite chroma

Self-adhesive resin cements were developed to reduce the number of application steps and technique sensitivity associated with conventional resin cements. Maxcem Elite is a two-paste, dual-cure resin cement which combines the conditioning, priming, and adhesive agents into a single application. Maxcem Elite contains a proprietary redox initiator system: an efficient dual-cure mechanism that allows the resin to set quickly in the absence of light curing. Moreover, this proprietary redox initiator system eliminates the inherent discoloration of BPO/tertiary amine initiator systems for more esthetic restorations. However, when compared to conventional resin cements, self-adhesive resins reportedly provided inferior bonding to both enamel [53]. Maxcem Elite chroma has a colour indicator added to its predecessor Maxcem Elite. The colour indicator is pink when two solutions are mixed and as the material goes into initial set or gel phase, the pink colour fades away and turns colorless indicating optimal time to remove any excess cement. This property is particularly beneficial for bracket bonding in orthodontics, as it tells us the time to remove flash without disturbing the set bracket position significantly. After removing the flash the composite can be command cured by light cure devise.

### Bracket bond failure

Bond failure at bracket-adhesive interface, rather than at enamel-adhesive interface, is caused by the low flexural strength of composite resins. Brackets bonded to enamel surfaces are temporary: they shall be removed after active treatment. Therefore, the primary orthodontic goal is to maintain sound, unblemished enamel surfaces after de-bonding. Enamel damage can be caused by phosphoric acid etching, bracket removal or cleaning of the teeth after de-bonding. Phosphoric acid etching complicates the removal of residual adhesive on the enamel after de-bonding, subsequently leading to surface scratches, cracking, and loss of sound enamel [48].

ARI score "5" means that bond failure site is at adhesive-enamel interface, while score "0" means that detachment occurs at adhesive-bracket base interface. In the present study, statistically significant differences were found in the ARI scores among the groups. ARI scores of 3 and 4 were predominantly seen in Maxcem Elite. This meant that when phosphoric acid etching was omitted, interfacial bonding between enamel and adhesive became the weakest link. However, when these adhesive materials were applied to etched enamel with an SEP, the ARI decreased. From the perspective of cleaning up the teeth after de-bonding, it is advantageous and preferred for residual adhesive to remain at bracket bases. This makes cleaning of the enamel surfaces easier and faster, with less risk of causing damage to the enamel [54]. In the present study, Maxcem Elite yielded the highest SBS and higher incidences of ARI scores of 3 and 4 that is, a lesser amount of residual adhesive remained on the teeth. If adequate shear bond strength is attained, benefits of low ARI scores outweigh those of high ARI scores: detachment at enamel-adhesive interface lowers the risk of enamel damage and hence the probability of enamel cracks

formation. But if both are achieved, that is, high SBS and high ARI like it were seen in maxcem elite group, it is highly desirable for an orthodontic adhesive. Hence it was demonstrated that Maxcem Elite chroma not only has an adequate SBS but also has a favourable de-bonding characteristics and that it can be considered as an alternative to total etch technique or self etch technique for bonding of brackets in orthodontics.

## Conclusion

The purpose of this in vitro study was to evaluate of the shear bond strength and de-bonding properties of self etch adhesive composite cement (Maxcem Elite Chroma) and self etching primer composite system (Transbond Plus SEP, 3M Unitek, Monrovia, Calif) used for orthodontic bracket bonding. The self etch adhesive resin cements eliminates the need of separate etching and priming thereby reducing the operating time by a significant amount. Sufficient research is not available with regard to whether self etching adhesives can be satisfactorily used in the field of orthodontics to bond the brackets. The SBS, the de-bonding properties and its effect on enamel demineralization have been documented rather elusively. Hence the current study was conducted to evaluate the same.

### The conclusions from this study are as follows

1. New self-etch, self-adhesive bonding system surprisingly showed high SBS as compared to self etch primer,
2. It also demonstrated a high ARI scores on the bracket surface which signifies that the de-bonding takes place mostly at tooth resin interface thereby reduces the chances of deleterious effects like crazing of enamel surface from de-bonding forces.
3. Both of the above properties are desirable for orthodontic bracket bonding and hence it can be considered as an alternative to traditional bonding systems

Within the limitations of this in vitro study, we drew the above mentioned conclusion. However, further in vitro and in vivo studies of these self-etch, self adhesive bonding systems are needed to obtain data and findings useful and important for clinical practice which can be focused to demonstrate following:

1. The effects of mineral structure of teeth and hand piece pressure on the SBS of different adhesive materials.
2. The effect of aging on the SBS of this new adhesive which can be checked for both in vivo and in vitro environments.
3. The surface characteristics of enamel before and after de-bonding when the self-etch, self adhesive bonding systems were used.

## References

1. Summitt JB, Robbins JW, Schwartz RS. Fundamentals of Operative Dentistry: A Contemporary Approach, 3rd ed. Hanover Park, Ill: Quintessence Publishing Co, Inc. 2006;184-210.
2. Bishara SE, Gordan VV, Von WL, Olson ME. Effect of an acidic primer on shear bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop.* 1998;114:243-7.
3. Barkmeier WW, Erickson RL. Shear bond strength of composite to enamel and dentin using Scotch bond multi-purpose. *Am J Dent.* 1994;7(3):175-9.
4. Bishara SE, Oonsombat C, Ajlouni R, Laffoon JF. Comparison of the shear bond strength of 2 self-etch primer/adhesive systems. *Am J Orthod Dentofacial Orthop.* 2004;125(3):348-50.
5. Bishara SE, Von WL, Laffoon JF, Warren JJ. Effect of a self-etch primer/adhesive on the shear bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop.* 2001;119(6):621-4.

6. Vicente A, Bravo LA, Romero M, Ortiz AJ, Canteras M. Shear bond strength of orthodontic brackets bonded with self-etching primers. *Am J Dent.* 2005;18(4):246-60.
7. Goracci C, Sadek FT, Monticelli F, Cardoso PE, Ferrari M. Microtensile bond strength of self-etching adhesive to enamel and dentin. *J Adhes Dent.* 2004;6(4):313-8.
8. Ostby AW, Bishara SE, Denehy GE, Laffoon JF, Warren JJ. Effect of self-etchant pH on the shear bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop.* 2008;134(2):203-8.
9. Bishara SE, Ostby AW, Laffoon JF, Warren JJ. The effect of modifying the self-etchant bonding protocol on the shear bond strength of orthodontic brackets. *Angle Orthod.* 2007;77(3):504-8.
10. Barkmeier WW, Erickson RL. Shear bond strength of composite to enamel and dentin using Scotch bond multi-purpose. *Am J Dent.* 1994;7(3):175-9.
11. Triolo PT Jr, Swift EJ, Mudgil A, Levine A. Effects of etching time on enamel bond strengths. *Am J Dent.* 1993;6(6):302-4.
12. Reynolds IR, von FJA. Direct bonding of orthodontic brackets-a comparative study of adhesives. *Br J Orthod.* 1976;3(3):143-6.
13. Buonocore MG. A simple method of increasing the adhesion of acrylic filling materials to enamel surfaces. *J Dent Res.* 1955;34(6):849-53.
14. Retief DH, Middleton JC, Jamison HC. Optimal concentration of phosphoric acid as an etching agent. Part III: Enamel wettability studies. *J Prost Dent.* 1985;53(1):42-6.
15. Fox NA, McCabe JF, Buckley JG. A critique of bond strength testing in orthodontics. *Br J Orthod.* 1994;21(1):33-43.
16. Bishara SE, VonWald L, Laffoon JF, Warren JJ. Effect of a self-etch primer/adhesive on the shear bond strength of orthodontic brackets. *Am J Orthod and Dentofacial Orthop.* 2001;119(6):621-4.
17. Bishara SE, Gordan VV, Von WL, Olson ME. Effect of an acidic primer on shear bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop.* 1998;114(3):243-7.
18. Bishara SE, Laffoon JF, Von WL, Warren JJ. The effect of repeated bonding on the shear bond strength of different orthodontic adhesives. *Am J Orthod Dentofacial Orthop.* 2002;121(5):521-5.
19. Cal-Neto JP, Miguel JA, Zanella E. Effect of a self-etching primer on shear bond strength of adhesive precoated brackets in vivo. *The Angle Orthod.* 2006;76(1):127-31.
20. Romano FL, Tavares SW, Nouer DF, Consani S, Magnani MB. Shear bond strength of metallic orthodontic brackets bonded to enamel prepared with self-etching primer. *Angle Orthod.* 2005;75(5):849-53.
21. Vilchis RJ, Yamamoto S, Kitai N, Yamamoto K. Shear bond strength of orthodontic brackets bonded with different self-etching adhesives. *Am J Orthod Dentofacial Orthop.* 2009;136(3):425-30.
22. Cehreli ZC, Keci D, Kocadereli I. Effect of self-etching primer and adhesive formulations on the shear bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop.* 2005;127(5):573-9.
23. Amra I, Samsodien G, Shaikh A, Lalloo R. Xeno III self-etching adhesive in orthodontic bonding: the next generation. *Am J Orthod Dentofacial Orthop.* 2007;131(2):160-e11.
24. Bishara SE, Ostby AW, Ajlouni R, Laffoon JF, Warren JJ. Early shear bond strength of a one-step self-adhesive on orthodontic brackets. *Angle Orthod.* 2006;76(4):689-93.
25. Bishara SE, Ostby AW, Ajlouni R, Laffoon JF, Warren JJ. Early shear bond strength of a one-step self-adhesive on orthodontic brackets. *The Angle Orthodontist.* 2006;76(4):689-93.
26. Abo-Hamar SE, Hiller KA, Jung H, Federlin M, Friedl KH, Schmalz G. Bond strength of a new universal self-adhesive resin luting cement to dentin and enamel. *Clin Oral Investig.* 2005;9(3):161-7.
27. De Munck J, Vargas M, Van LK, Hikita K, Lambrechts P, Van MB. Bonding of an auto-adhesive luting material to enamel and dentin. *Dental Mater.* 2004;20(10):963-71.
28. Minick GT, Oesterle LJ, Newman SM, Shellhart WC. Bracket bond strengths of new adhesive systems. *Am J Orthod Dentofacial Orthop.* 2009;135(6):771-6.
29. Vicente A, Bravo LA, Romero M, José Ortiz A, Canteras M. A comparison of the shear bond strength of a resin cement and two orthodontic resin adhesive systems. *Angle Orthod.* 2005;75(1):109-13.
30. Lührs AK, Guhr S, Schilke R, Borchers L, Geurtsen W, Günay H. Shear bond strength of self-etchadhesives to enamel with additional phosphoric acid etching. *Oper dent.* 2008;33(2):155-62.
31. Walter R, SWIFT, JR EJ, Boushell LW, Braswell K. Enamel, dentin bond strengths of a new self-etch adhesive system. *J Esthet Restor Dent.* 2011;23(6):390-6.
32. Radovic I, Monticelli F, Goracci C, Vulicevic ZR, Ferrari M. Self-adhesive resin cements: a literature review. *J Adhe Dent.* 2008;10(4):252-8.
33. Ferracane JL, Stansbury JW, Burke FJ. Self-adhesive resin cements—chemistry, properties and clinical considerations. *J Oral Rehabil.* 2011;38(4):295-314.
34. Fleming PS, Johal A, Pandis N. Self-etch primers and conventional acid-etch technique for orthodontic bonding: a systematic review and meta-analysis. *Am J Orthod Dentofacial Orthop.* 2012;142(1):83-94.
35. Nakamura T, Wakabayashi K, Kinuta S, Nishida H, Miyamae M, Yatani H. Mechanical properties of new self-adhesive resin-based cement. *J Prosthodont Res.* 2010;54(2):59-64.
36. Chu CH, Ou KL, Dong DR, Huang HM, Tsai HH, Wang WN. Orthodontic bonding with self-etching primer and self-adhesive systems. *Eur J Orthod.* 2011;33(3):276-81.
37. Al-Suleiman M, Baba F, Sawan MN, Suliman A. Mechanical Evaluation of the Effect of Reducing Phosphoric Acid Concentrations and Etching Duration on the Bond Strength of Orthodontic Brackets. *J Dent, Oral Disord & Therapy.* 2014;2(2):1-5.
38. Alkis H, Turkkahraman H, Adanir N. Micro leakage under orthodontic brackets bonded with different adhesive systems. *Eur J Dent.* 2015;9(1):117.
39. Hellak A, Ebeling J, Schauseil M, Stein S, Roggendorf M, Korbmacher-Steiner H. Shear bond strength of three orthodontic bonding systems on enamel and restorative materials. *Bio Med Res Int.* 2016.
40. Hattar S, Hatamleh MM, Sawair F, Al-Rabab'ah M. Bond strength of self-adhesive resin cements to tooth structure. *Saudi Dent J.* 2015;27(2):70-4.
41. Ongkowitzjaja F, Soegiharto BM, Purbati M. A comparison of orthodontic bracket shear bond strength on enamel deproteinized by 5.25% sodium hypochlorite using total etch and self-etch primer. *J Phys Conf Ser.* 2017.
42. Scougall-Vilchis RJ, Hotta Y, Yamamoto K. Examination of six orthodontic adhesives with electron microscopy, hardness tester and energy dispersive X-ray microanalyzer. *Angle Orthod.* 2008;78(4):655-61.
43. Scougall Vilchis RJ, Ohashi S, Yamamoto K. Effects of 6self-etching primers on shear bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop.* 2009;135(4):424.e1-7.
44. Scougall VRJ, Yamamoto S, Kitai N, Yamamoto K. Shear bond strength of orthodontic brackets bonded with different self-etching adhesives. *Am J Orthod Dentofacial Orthop.* 2009;136(3):425-30.
45. Kanemura N, Sano H, Tagami J. Tensile bond strength to and SEM evaluation of ground and intact enamel surfaces. *J Dent.* 1999; 27(7):523-30.
46. Arhun N, Arman A, Sesen C, Karabulut E, Korkmaz Y, Gokalp S. Shear bond strength of orthodontic brackets with 3 self-etch adhesives. *Am J Orthod Dentofacial Orthop.* 2006;129(4):547-50.
47. Eminkahyagil N, Korkmaz Y, Gokalp S, Baseren M. Shear bond strength of orthodontic brackets with newly developed antibacterial self-etch adhesive. *Angle Orthod.* 2005;75(5):843-48.
48. Kim MJ, Lim BS, Chang WG, Lee YK, Rhee SH, Yang HC. Phosphoric acid incorporated with acidulated phosphate fluoride gel etchant effects on bracket bonding. *Angle Orthod.* 2005;75(5):678-84.
49. Di Francescantonio M, de Oliveira MT, Shinohara MS, Ambrosano GMB, Giannini M. Bond strength evaluation of self-etch and total-etch adhesive systems on intact and ground human enamel. *Braz J Oral Sci.* 2007;6(23):1462-6.
50. Kiremitci A, Yalcin F, Gokalp S. Bonding to enamel and dentin using self-etching adhesive systems. *Quintessence Int.* 2004; 35(5):367-70.
51. De Munck J, Vargas M, Van LK, Hikita K, Lambrechts P, Van Meerbeek B. Bonding of an auto-adhesive luting material to enamel and dentin. *Dent Mater.* 2004;20(10):963-71.
52. Yang B, Ludwig K, Adelung R, Kern M. Micro-tensile bond strength of three luting resins to human regional dentin. *Dent Mater.* 2006;22(1):45-56.
53. İşman E, Karaarslan EŞ, Okşayan R, Tunçdemir AR, Üşümez S, Adanir N, et al. Inadequate shear bond strengths of self-etch, self-adhesive systems for secure orthodontic bonding. *Dent Mater J.* 2012;31(6):947-53.
54. Usume S, Buyukyilmaz T, Karaman AI. Effect of light-emitting diode on bond strength of orthodontic brackets. *Angle Orthod.* 2004;74(2):259-63.